

Huntonit AS

Postboks 2

NO-4701 Vennesla

Norge

Emission measurements according to M1

(3 appendices)

Assignment

Emission measurement according to “M1 Emission Classification of Building Materials: Protocol for Chemical and Sensory Testing of Building Materials”, version 15.11.2017, after 28 days of conditioning regarding volatile organic compounds, carcinogenic compounds (EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), formaldehyde, ammonia and sensory acceptability.

Product/test specimen

Table 1.

Product type:	Wood fiber board
Product name:	Huntonit ferdigmalt vegg
Manufacturer:	Huntonit AS, Norge
Manufacturing date:	2021-05-30
Sampling date:	2021-06-01
Size of sample, packaging:	6 pieces 600 x 1200 mm, wrapped together in plastic foil
Arrived at RISE:	2021-06-08
Test specimen preparation:	<p>Wall scenario is used for the testing.</p> <p>Chemical testing: Four pieces of 50 x 13.5 cm were cut out. They were placed, two and two, back-to-back and the edges were sealed with aluminium tape leaving a total exposed surface area of 0.27 m².</p> <p>Sensory testing: Four pieces, 50 x 85 cm were cut out. They were placed, two and two, back-to-back and the edges were sealed with aluminium tape leaving a total exposed surface area of 1.7 m².</p>
Deviation from protocol:	No
Test period started, date:	2021-06-10
Conditions during ageing:	23 ± 2 °C, 50 ± 5 % RH
Emission samplings, date:	2021-07-08

RISE Research Institutes of Sweden AB

Postal address

Box 857
501 15 BORÅS
SWEDEN

Office location

Brinellgatan 4
504 62 Borås
SWEDEN

Phone / Fax / E-mail

+46 10-516 50 00
+46 33-13 55 02
info@ri.se

This report may not be reproduced other than in full, except with the prior written approval of the issuing laboratory.



Methods

The specimens were conditioned outside the testing chambers in a room with controlled climate conditions of 23 ± 2 °C and 50 ± 5 % RH. The specimens were placed in the chambers three days before the measurements of the chemical emission and the sensory evaluation.

Table 2.

Chamber conditions of the test of chemical emissions

Test chamber volume:	0.27 m ³ , stainless steel
Temperature:	23 ± 1 °C
Relative Humidity:	50 ± 3 % RH
Air exchange rate:	0.5 h ⁻¹
Air velocity at specimen surface:	0.1 – 0.3 m/s
Area of sample:	0.27 m ²
Area specific air flow rate:	0.5 m ³ /m ² h

Table 3.

Chamber conditions of the test of sensory acceptability

Test chamber volume:	1.0 m ³ , stainless steel
Temperature:	23 ± 1 °C
Relative Humidity:	50 ± 3 % RH
Supply air flow rate:	0.9 l/s = 3.2 m ³ /h
Area of sample:	1.7 m ²

Table 4.

Emission sampling and analytical methods

Test	Sampling method	Adsorbent	Sampling volume (litre)	Analysis method / Quantification	Detection limit
VOC	ISO 16000-9:2006 ¹	Tenax TA	2.7 – 6.3	ISO 16000-6 ² / FID quantification	1 µg/m ³
Formaldehyde	ISO 16000-9:2006 ¹	DNPH	33	SP 2303 ³ /HPLC-UV	0.03 µg/sampler
Ammonia	ISO 16000-9:2006 ¹	Treated silica gel	265 – 325	Liquid chromatograph with conductivity detector ⁴	1.0 µg/sampler
Sensory evaluation	ISO 16000-28:2012 ⁵	--	--	Acceptability, Untrained panel of min 15 persons	--

¹⁾ In accordance with ISO 16000-9:2006 and M1 protocol.

²⁾ In accordance with ISO 16000-6:2011 and M1 protocol.

³⁾ In accordance with ISO 16000-3:2001.

⁴⁾ Not accredited method.

⁵⁾ In accordance with M1 protocol, not accredited method.

Tenax TA was used as adsorption medium for VOC. The tubes were thermally desorbed and analysed in accordance to ISO 16000-6:2011 (Determination of volatile organic compounds in indoor and test chamber air by active sampling on Tenax TA sorbent, thermal desorption and gas chromatography using MS/FID). This means an analysis in a gas chromatograph and detection with a flame ionisation detector (FID) and mass selective detector (MS). The FID signals are used for compound quantification. The TVOC is quantified as toluene equivalents. The mass selective detector is used for identification of compounds. The capillary column used is coated with 5% phenyl/ 95 % methylpolysiloxane. Tenax TA was also used as adsorption

medium for testing of volatile carcinogenic compounds, according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), (exclusive formaldehyde), 0.001 mg/m³ and above.

The sampling of formaldehyde was carried out with DNPH samplers. The samplers were analysed according to SP method 2302, similar to ISO 16000-3:2011(Indoor air--Part 3: Determination of formaldehyde and other carbonyl compounds – Active sampling method), which means analysis on a liquid chromatograph with absorbance detector.

The sampling of ammonia was carried out with silicagel treated adsorbent tubes and analysis on a liquid chromatograph with conductivity detector.

Minimum two subsequent samples were taken for the determination of VOC, formaldehyde and ammonia respectively.

Results

The results relate only to the items tested.

Decision rule: When comparing the measured results and requirement level, the average value of the measured results has been compared with the requirement level. No account is taken to the measurement uncertainty.

The results of the chemical testing are expressed as area specific emission rates and as concentrations in a model room. The model room has a base area of 3 m x 4 m and a height of 2.5 m, with an air exchange rate of 0.5 h⁻¹. The wall area is 31.4 m², floor area is 12 m², small area, like a door, is 1.6 m² and very small area, like sealant, is 0.2 m². Wall area is used for the calculation of the concentrations.

Calculation of the concentration from the emission rate:

$$Conc = \frac{SER_A \times A}{n \times V}$$

Conc = concentration of a VOC in the model room, in µg/m³
 SER_a = area specific emission rate, in µg/m²h
 A = area of sample, in m²
 n = air exchange rate, in changes per hour
 V = volume of the model room, in m³

Table 5.

Results of the chemical testing of the sample **Huntonit ferdigmalt vegg**, after 28 days

Compound	Concentration in model room mg/m ³	Emission rate mg/m ² h	Criteria M1 mg/m ² h
TVOC ⁶	0.090	0.043	< 0.2
Carcinogens	< 0.001	< 0.001	< 0.001
Single VOC (µg/m ³)	< EU-LCI	--	≤ EU-LCI
Formaldehyde	0.001	< 0.001	< 0.05
Ammonia ⁷	0.005	0.002	< 0.03

⁶) The TVOC is the sum of the individual concentration ≥ 5 µg/m³ in model room.

⁷) Not accredited method.

Table 6.

Results of the sensory acceptability evaluation of the sample **Huntonit ferdigmalt vegg**, after 28 days

Evaluator	Sensory evaluation	Criteria M1
1	0.50	
2	0.82	
3	0.87	
4	0.91	
5	0.99	
6	0.73	
7	0.96	
8	0.92	
9	1.00	
10	0.40	
11	0.04	
12	0.00	
13	0.78	
14	0.90	
15	0.11	
Arithmetic mean of acceptability ⁸	0.66	$\geq + 0.0$
Standard deviation	0.36	
90 % confidence interval of arithmetic mean	0.15	≤ 0.2

⁸⁾ Not accredited method.

The empty sensory test chamber acceptability was determined 2021-07-05. The mean acceptability vote of the empty chamber was > 0.8 .

Interpretation of the results

The tested product **Huntonit ferdigmalt vegg** complies with all the requirements of M1 for the tested parameters.

Detailed results

Table 7.

Detailed results (emission rates) of the chemical testing after 28 days

Sample	TVOC (mg/m ² h) as toluene equivalents between C ₆ -C ₁₆	Formaldehyde (mg/m ² h)	Ammonia (mg/m ² h)	Carcinogens (mg/m ² h) between C ₆ -C ₁₆
1	0.043	< 0.001	< 0.002	< 0.001
2	0.043	< 0.001	0.003	< 0.001

Table 8.

 Single VOCs above 5 µg/m³ in the model room (wall area scenario)

Single VOCs	CAS number	Retention time (min)	ID ⁹	Emission rate (µg/m ² h)	Concentration (µg/m ³)
Single VOCs C₆-C₁₆:	--	6.2 – 37.9			
Hexanal	66-25-1	11.7	B	12	25
Ethanol, 2-(2-butoxyethoxy)-	112-34-5	25.9	B	11	23
Dipropylene glycol n-butyl ether	29911-28-2	27.6+27.7	B	20	42
TVOC	--	6.2 – 37.9	B	43	90
Volatile Carcinogens ¹⁰		6.2 – 37.9			
No substances detected	--	--	B	< 1	< 1
Single VOC outside C₆ – C₁₆:					
VVOC (< C₆) ¹¹		4.5 – 6.2			
Acetone	67-64-1	4.8	B	8	16
SVOC (C₁₆ – C₂₂) ¹²		37.9 – 51.3			
No substances detected	--	--	B	< 2	< 5

⁹⁾ ID: A = quantified compound specific, B = quantified as toluene-equivalent

¹⁰⁾ Volatile carcinogens = VOCs according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B

¹¹⁾ VVOC = very volatile organic compounds, as defined in ISO 16000-6 (not accredited)

¹²⁾ SVOC = semi-volatile organic compounds, as defined in ISO 16000-6 (not accredited)

TVOC is the sum of all individual substances with concentrations ≥ 5 µg/m³ in the model room (in toluene equivalents). Level of identification of compounds is 100 % for all compounds ≥ 5 µg/m³

Table 9.

 Detected EU LCI-compounds ≥ 5 µg/m³ quantified by compound specific response factor

Single VOCs	CAS number	Retention time (min)	ID ⁹	Concentration (µg/m ³)	EU LCI _i (Dec 2020) (µg/m ³)
Hexanal	66-25-1	11.7	A	42	900
Ethanol, 2-(2-butoxyethoxy)-	112-34-5	25.9	A	57	350
Dipropylene glycol n-butyl ether	29911-28-2	27.6+27.7	A	76	250

⁹⁾ ID: A = quantified compound specific, B = quantified as toluene-equivalent

Measurements uncertainty

The expanded measurement uncertainty of VOC result is 15 % (rel) and formaldehyde is 30 % (rel). For ammonia the measurement uncertainty is estimated to 20 % (rel).

See Appendix 1 for a gas chromatogram from the VOC determination and Appendix 2 for a photo of a test specimen. Appendix 3 is the Sampling report received from the customer.

RISE Research Institutes of Sweden AB
Chemistry, Biomaterials and Textiles - Chemical and Biological Safety

Performed by

Examined by

Ulrika Johansson

Marcus Gjertz

Appendices


1. Gas Chromatogram
2. Photo of a test specimen
3. Sampling report

Appendix 1

Gas chromatogram

Sample: **Huntonit ferdigmalt vegg**, after 28 days

Abundance

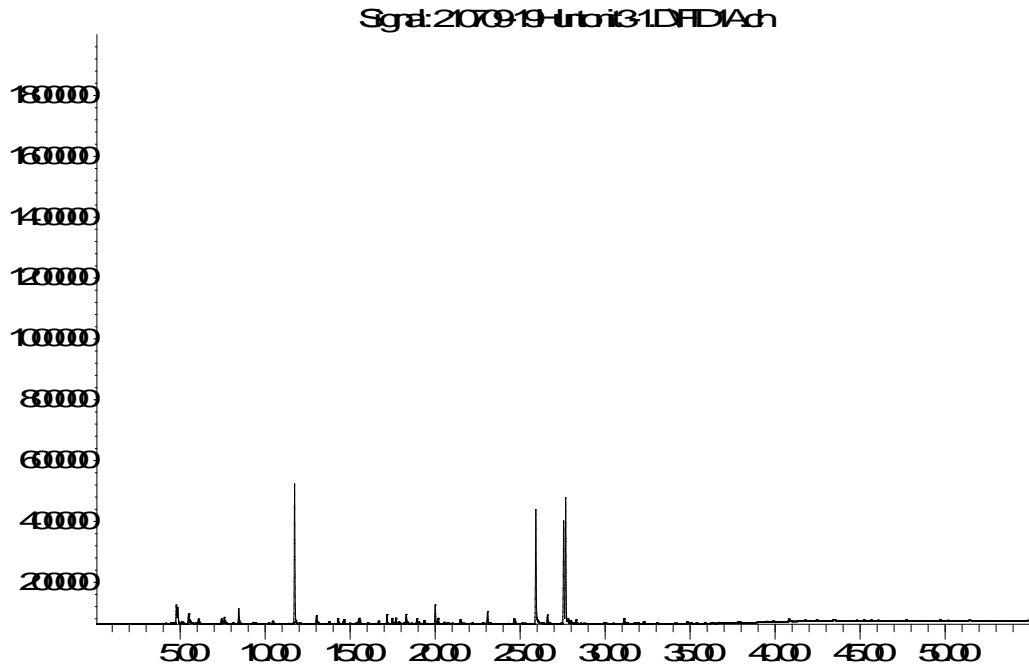

Time >

TVOC between C₆ and C₁₆, means compounds eluting between 6.2 and 37.9 minutes.

Appendix 2

Photo of a test specimen

Specimens for the chemical emission

Appendix 3

Sampling Report

<p>Sampler (Name, Company, contact info):</p> <p>HUNTONIT AS Kjell Torland Venneslaveien 233 4700 VENNESLA NORGE</p> <p>NO 914 801 958 MVA</p>	<p>Manufacturer of the product (Company, address):</p> <p>HUNTONIT AS Venneslaveien 233 4700 VENNESLA Norge</p>
<p>Name of product:</p> <p>Huntonit ferdigmalt vegg</p>	<p>Type of product:</p> <p>Wood fiber board</p>
<p>Manufacturing Date:</p> <p>30.05.2021</p>	<p>Batch No:</p> <p>01.06.21</p>
<p>Date of sampling:</p> <p>01.06.21</p>	<p>Amount/size of material sampled:</p> <p>600x1200</p> <p>Packing material: Plastic</p>
<p>Sample is taken from:</p> <p>Production line <input type="checkbox"/></p> <p>Stock / Storage <input checked="" type="checkbox"/></p> <p>Miscellaneous <input type="checkbox"/></p> <p>-where, specify:</p>	<p>How was the product stored before sampling?</p> <p>Intermediate storage</p>
<p>If a sub-sample was collected from a larger material amount, describe how the sub-sample was taken:</p>	
<p>Observations and remarks:</p>	
<p>Confirmation I hereby confirm that the sample was selected, taken and packed in accordance with the instructions.</p>	
<p>Date: 01.06.21</p>	<p>Signature: Kjell Torland</p>